


Analysis of structural properties of Ca-doped BaTiO₃ ceramics

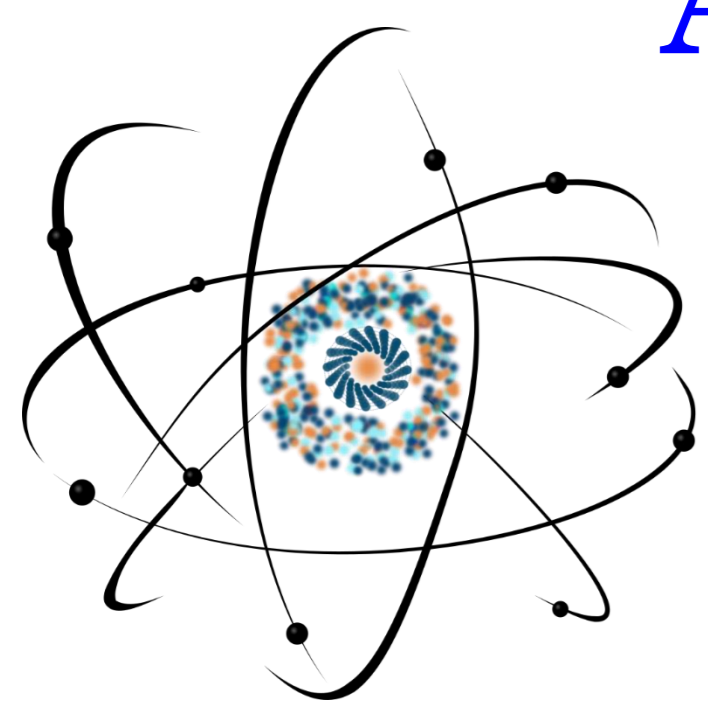

H. Klym^{1*}, I. Karbovnyk², Yu. Kostiv¹

¹Lviv Polytechnic National University, Bandera str., 12, Lviv-79013, Ukraine

*klymha@yahoo.com, halyna.i.klym@lpnu.ua


²Ivan Franko National University of Lviv, Tarnavskogo str., 107, Lviv-79017, Ukraine



Introduction

Barium titanate (BaTiO₃) is a displacement-type ferroelectric perovskite, widely studied for its basic properties and extensive applications [1]. In this materials defects originated by the preparation method. The aim of this work is study of free-volume defects in undoped and Ca-doped BaTiO₃ ceramics using positron annihilation lifetime (PAL) spectroscopy in comparison with scanning electron microscopy (SEM) method.


EXPERIMENTAL: Positron Annihilation Lifetime (PAL) Spectroscopy

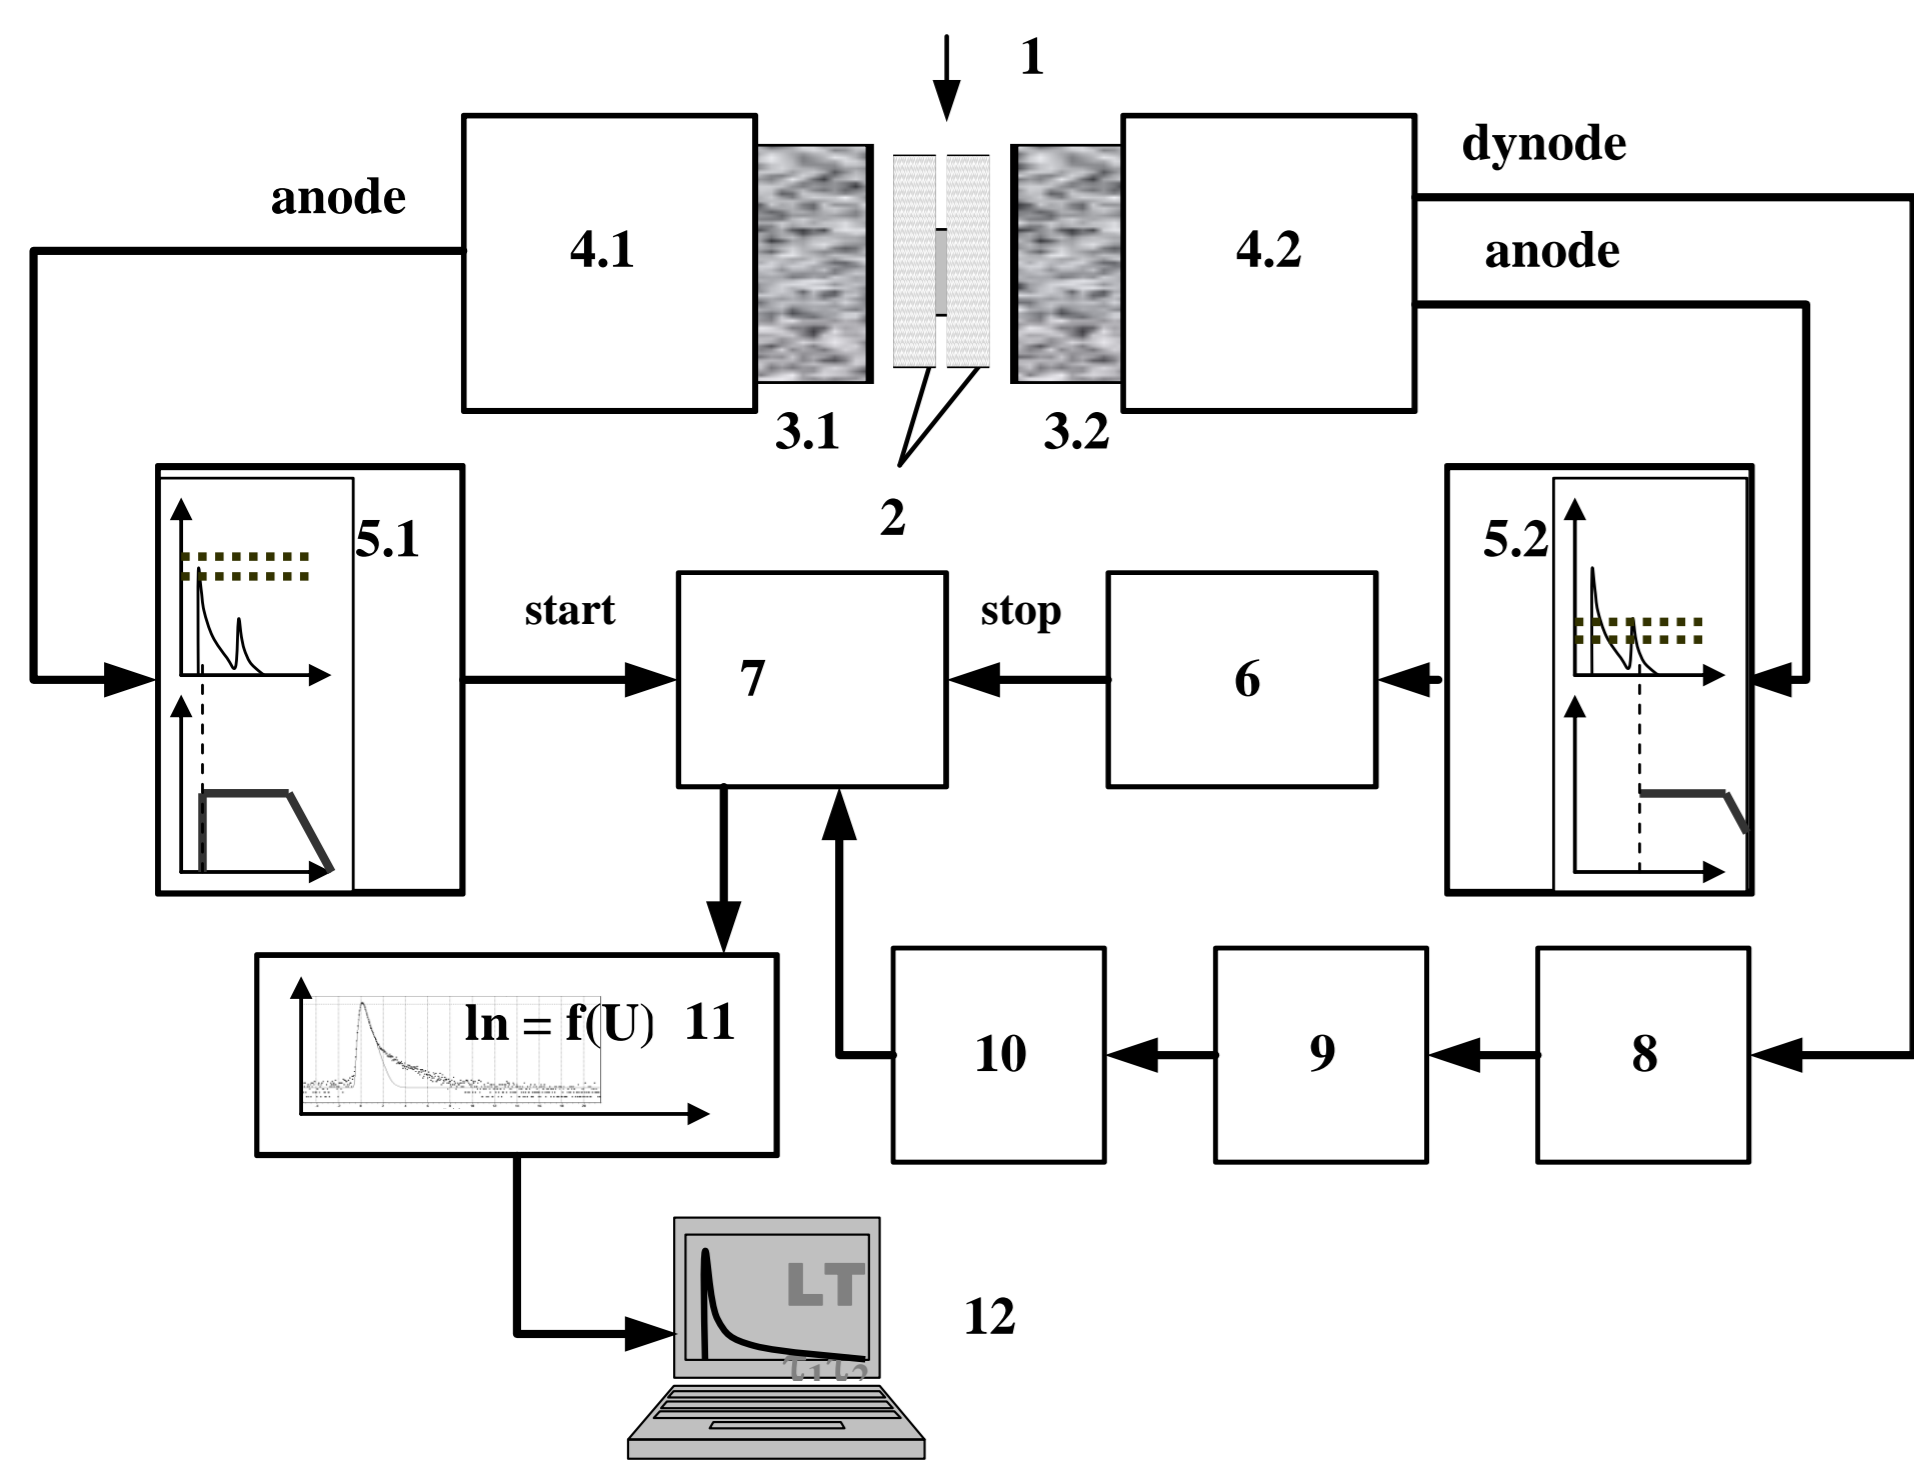

Block-scheme of conventional sample-source "sandwich" arrangement for PAL measurements using the ORTEC apparatus:


- 1 – foil-covered ²²Na source,
- 2 – two identical samples,
- 3.1 and 3.2 – scintillators of γ -quanta,
- 4.1 and 4.2 – photomultipliers,
- 5.1 and 5.2 – constant fraction discriminators,
- 6 – delay line,
- 7 – time-pulse height converter,
- 8 – preamplifier,
- 9 – amplifier,
- 10 – single channel analyzer,
- 11 – multichannel analyzer,
- 12 – personal computer.

MATHEMATICAL TREATMENT of PAL DATA: LT computer program, 2-component fitting procedure

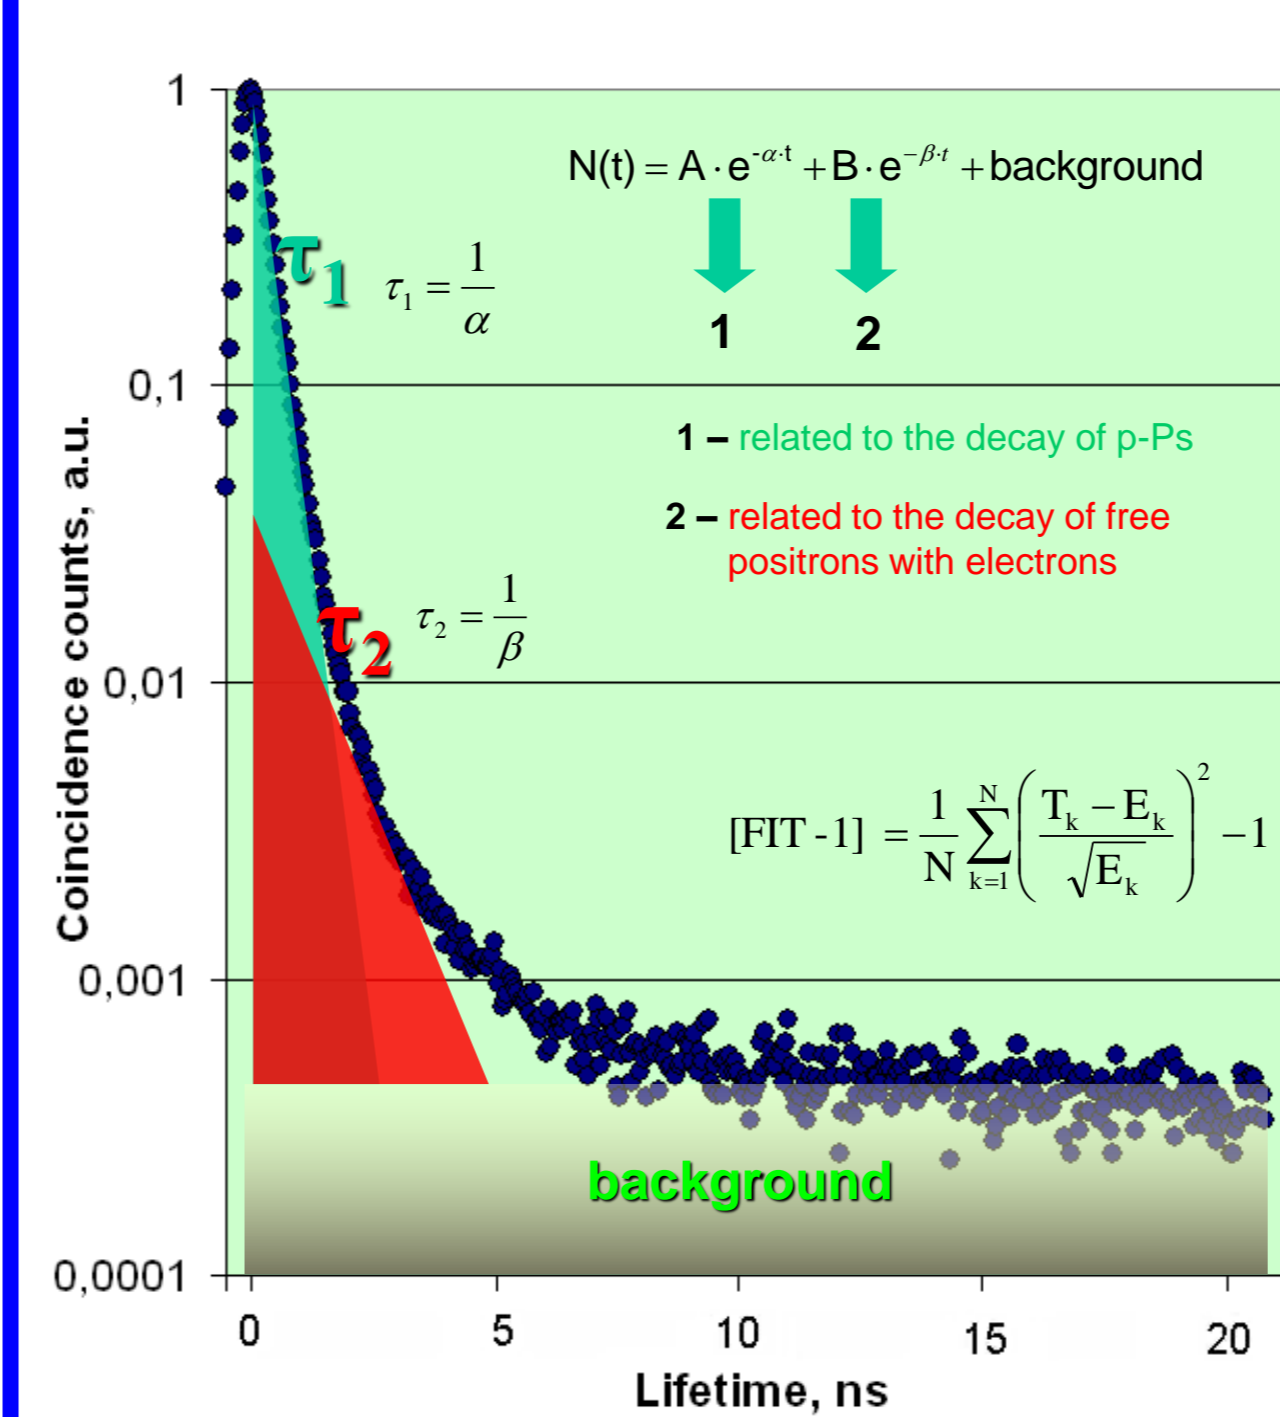

$\tau_{av.} = \frac{\tau_1 I_1 + \tau_2 I_2}{I_1 + I_2}$	Mean positron lifetime: reflects cumulative defect environment prevailing in sample
Lifetime τ_b associated with the positron trapping in defect-free bulk	$\tau_b = \frac{I_1 + I_2}{\tau_1 + \tau_2}$
$\kappa_d = \frac{I_2}{I_1} \left(\frac{1}{\tau_b} - \frac{1}{\tau_2} \right)$	Positron trapping rate in defects
$\tau_2 - \tau_b$	Size measure of extended defects where positrons are trapped
Represents the nature of defects	τ_2 / τ_b

Typical microstructure of ceramics

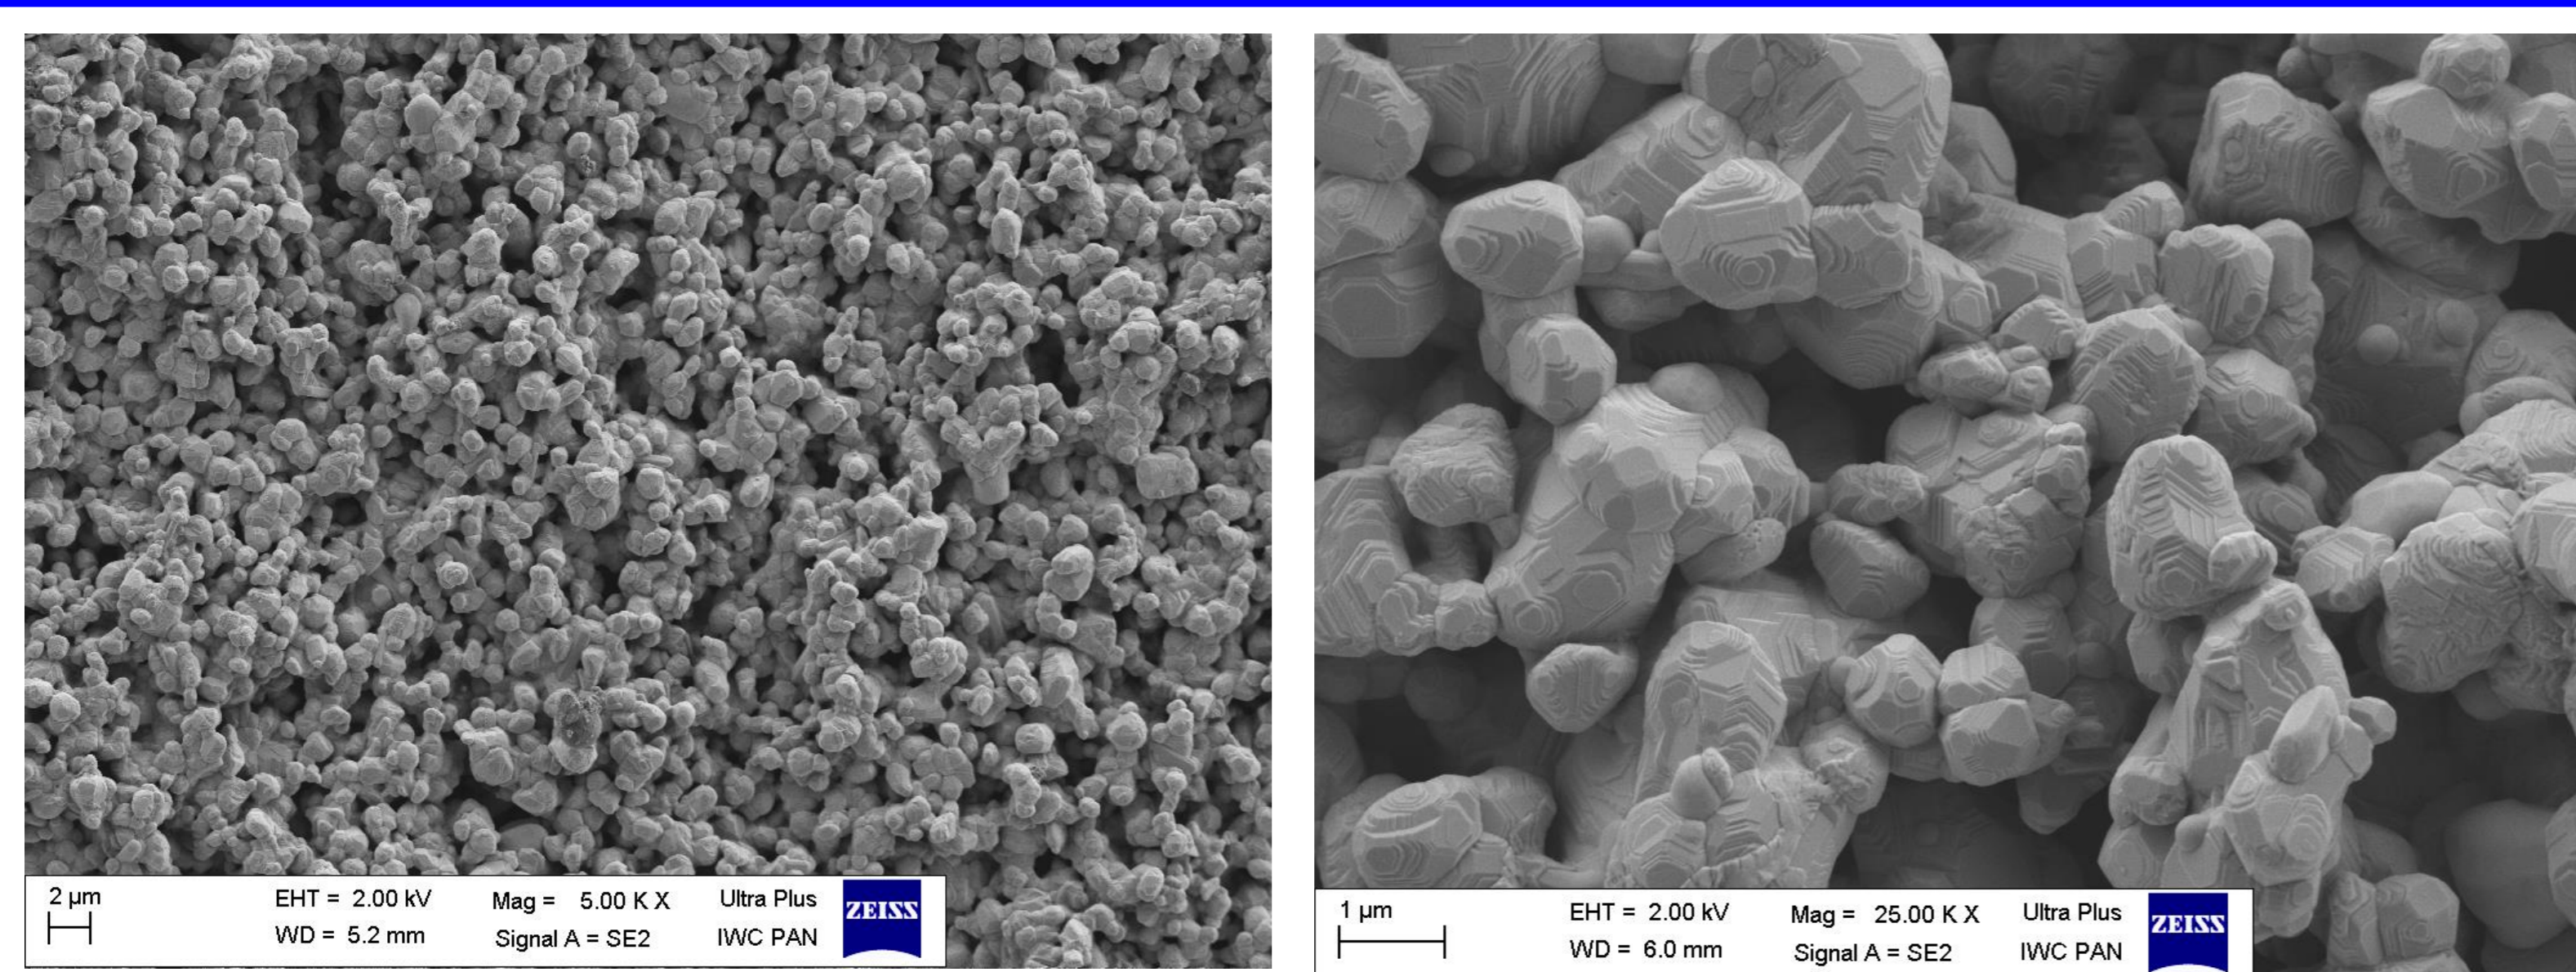


Undoped BaTiO₃ ceramics and doped with 5, 10 and 15 mol% of Ca were sintered at 1250 °C. The PAL measurements were performed with an ORTEC spectrometer using ²²Na source placed between two sandwiched ceramic samples. The obtained data were treated with LT computer program, the best results corresponding to two-component fitting procedures. The numerical values of trapping parameters (positron lifetime in defect-free bulk τ_b , average positron lifetime $\tau_{av.}$ and positron trapping rate of defect κ_d) were calculated using short and long positron-trapping lifetimes τ_1 and τ_2 , as well as component intensities I_1 and I_2 ($I_1 + I_2 = 1$). The difference ($\tau_2 - \tau_b$) can be accepted as a size measure of extended defects where positrons are trapped, the τ_2/τ_b ratio represents the nature of these defects.

RESULTS: PAL characteristics

Sample	Fitting parameters				Components input	
	τ_1 , ns	I_1 , a.u.	τ_2 , ns	I_2 , a.u.	$\tau_{av.}^1$, ns	$\tau_{av.}^2$, ns
BaTiO ₃	0.151	0.78	0.315	0.22	0.12	0.07
BaTiO ₃ + 5 mol% Ca	0.152	0.80	0.319	0.20	0.12	0.06
BaTiO ₃ + 10 mol% Ca	0.155	0.84	0.324	0.16	0.13	0.05
BaTiO ₃ + 15 mol% Ca	0.143	0.75	0.286	0.25	0.11	0.07

Sample	Positron trapping modes				
	$\tau_{av.}$, ns	τ_b , ns	κ_d , ns ⁻¹	$\tau_2 - \tau_b$, ns	τ_2/τ_b
BaTiO ₃	0.187	0.170	0.76	0.14	1.85
BaTiO ₃ + 5 mol% Ca	0.185	0.170	0.69	0.15	1.88
BaTiO ₃ + 10 mol% Ca	0.183	0.169	0.56	0.16	1.93
BaTiO ₃ + 15 mol% Ca	0.178	0.163	0.86	0.12	1.76

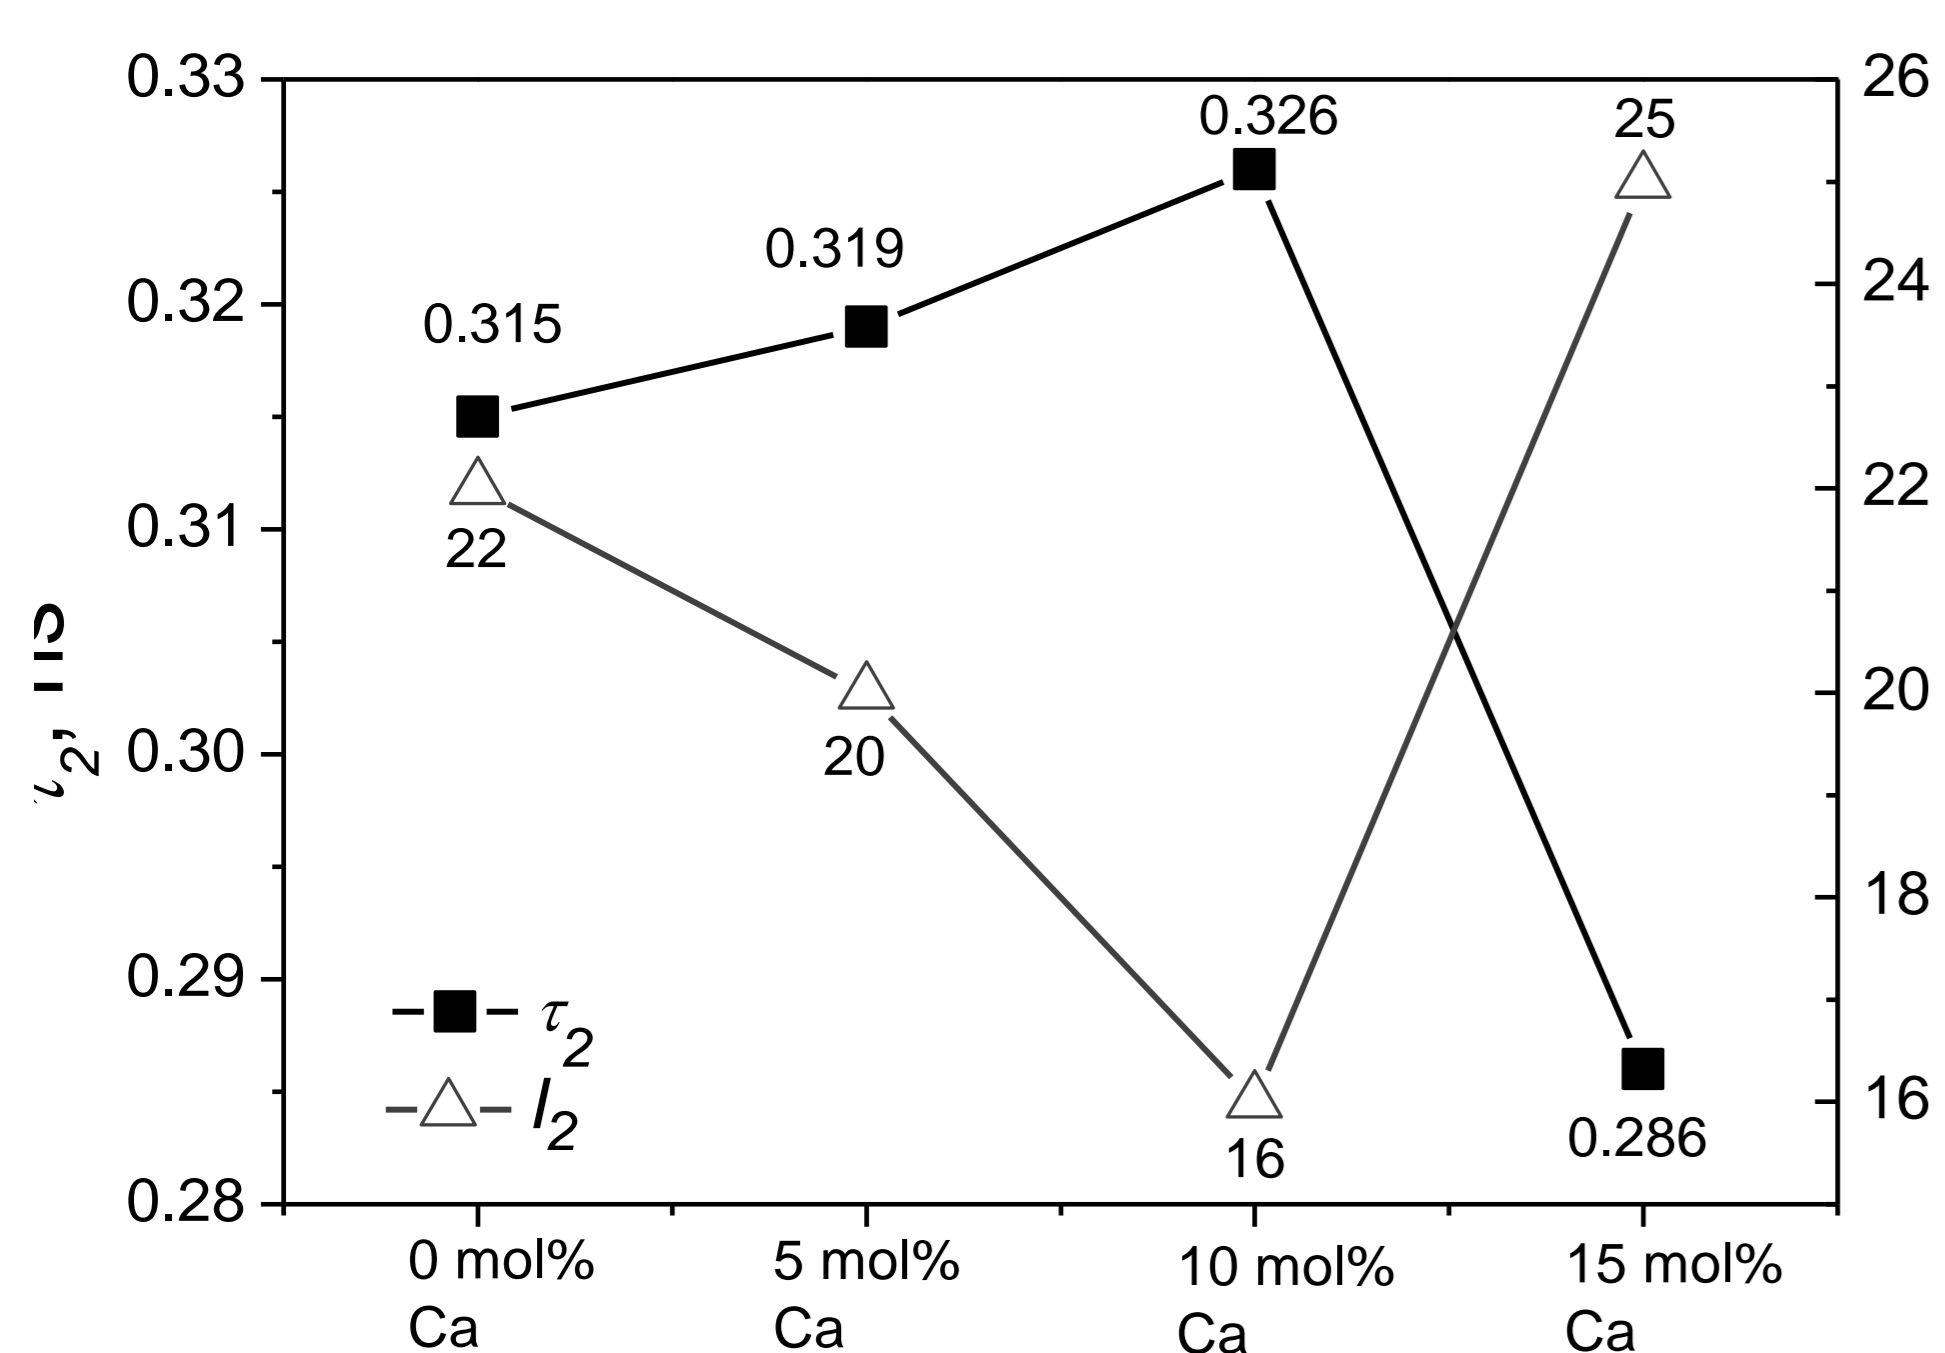

In respect to SEM investigations, typical ceramic samples show grain-porous microstructure and assemblies of fractional grains. By accepting two-state positron trapping model, for polycrystalline ceramic materials the short lifetime of $\tau_1 \sim 0.15$ ns is generally attributed to the free annihilation of positrons. This value also correlated with theoretically calculated free positron lifetime in BaTiO₃. The obtained value is closed to BaTiO₃ single crystal. The second lifetime τ_2 arises from annihilation of positrons at defect sites. The presently observed values of $\tau_2 \sim 0.32$ ns which is believed to come from the annihilation of positrons at vacancy complexes formed between the oxygen vacancies and the metal ion vacancies. It is obvious from Figure that τ_2 increases with rise of Ca amount in BaTiO₃ ceramics from 5 to 10 mol% and decreases in samples with 15 mol% of Ca. the intensity I_2 decreases from 22 to 16 % and increases to 25 % in samples with 15 mol% of Ca.

This indicates that doping of Ca results in increasing of the size of free-volume defects in ceramics and decreasing of their amount. So, process of agglomeration of defects is take place at posing of BaTiO₃ ceramics By Ca in amount of 5 and 10 mol%, while future increasing the Ca content to 15 mol% leads to fragmentation of free-volume defects.

